



PHY 712 Electrodynamics

11-11:50 AM MWF Olin 103

Notes for Lecture 33:

Special Topics in Electrodynamics:

Electromagnetic aspects of superconductivity



21	Fri: 03/25/2022	Chap. 9	Radiation from localized oscillating sources	#18	03/30/2022
22	Mon: 03/28/2022	Chap. 9	Radiation from oscillating sources		
23	Wed: 03/30/2022	Chap. 9 & 10	Radiation and scattering	#19	04/01/2022
24	Fri: 04/01/2022	Chap. 11	Special Theory of Relativity	#20	04/04/2022
25	Mon: 04/04/2022	Chap. 11	Special Theory of Relativity	#21	04/06/2022
26	Wed: 04/06/2022	Chap. 11	Special Theory of Relativity		
27	Fri: 04/08/2022	Chap. 14	Radiation from moving charges	#22	04/11/2022
28	Mon: 04/11/2022	Chap. 14	Radiation from accelerating charged particles	#23	04/18/2022
29	Wed: 04/13/2022	Chap. 14	Synchrotron radiation		
	Fri: 04/15/2022	No class	<i>Holiday</i>		
30	Mon: 04/18/2022	Chap. 14 & 15	Thompson and Compton scattering	#24	04/20/2022
31	Wed: 04/20/2022	Chap. 15	Radiation from collisions of charged particles		
32	Fri: 04/22/2022	Chap. 13	Cherenkov radiation		
33	Mon: 04/25/2022		Special topic: E & M aspects of superconductivity		
34	Wed: 04/27/2022		Review		
35	Fri: 04/29/2022		Review		

Important dates: Final exams available Apr. 29; due May 9
Outstanding work due May 9

What will you do after May 9?

Relax a minute or two

Several of you will want to start preparing for the Qualifier Exams which will be administered (tentative dates):

Monday, June 13 to Thursday, June 16 during the hours 1:00 – 4:00 pm.



Special topic: Electromagnetic properties of superconductors

Ref: D. Teplitz, editor, Electromagnetism – paths to research, Plenum Press (1982); Chapter 1 written by Brian Schwartz and Sonia Frota-Pessoa


History:

1908 H. Kamerlingh Onnes successfully liquified He

1911 H. Kamerlingh Onnes discovered that Hg at 4.2 K has vanishing resistance

1957 Theory of superconductivity by Bardeen, Cooper, and Schrieffer

The surprising observation was that electrical resistivity abruptly dropped when the temperature of the material was lowered below a critical temperature T_c .

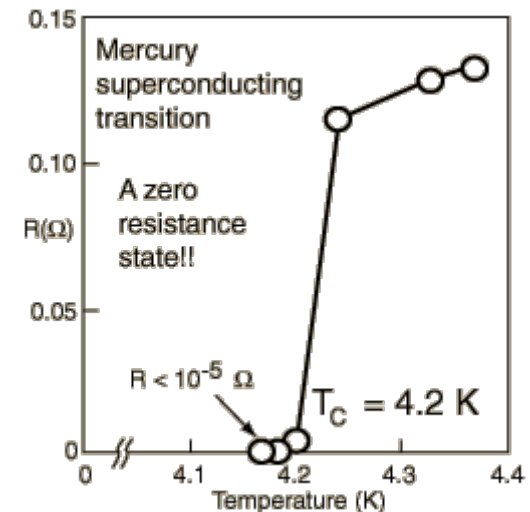

Fritz London 1900-1954



Fritz London, 1947, photo: Lotte Meitner-Graf

Fritz London, one of the most distinguished scientists on the Duke University faculty, was an internationally recognized theorist in Chemistry, Physics and the Philosophy of Science. He was born in Breslau, Germany (now Wroclaw, Poland) in 1900. In 1933 he was

He immigrated to the United States in 1939, and came to Duke University, first as a Professor of Chemistry. In 1949 he received a joint appointment in Physics and Chemistry and became a James B. Duke Professor. In 1953 he became the 5th recipient of the Lorentz medal, awarded by the Royal Netherlands Academy of Sciences, and was the first American citizen to receive this honor. He died in Durham in 1954.

<https://phy.duke.edu/about/history/historical-faculty/fritz-london>



Some phenomenological theories < 1957 thanks to F. London

Drude model of conductivity in "normal" materials

$$m \frac{d\mathbf{v}}{dt} = -e\mathbf{E} - m \frac{\mathbf{v}}{\tau}$$

$$\mathbf{v}(t) = \mathbf{v}_0 e^{-t/\tau} - \frac{e\mathbf{E}\tau}{m}$$

Note: Equations are in cgs Gaussian units.

$$\mathbf{J} = -ne\mathbf{v}; \quad \text{for } t \gg \tau \quad \Rightarrow \quad \mathbf{J} = \frac{ne^2\tau}{m}\mathbf{E} \equiv \sigma\mathbf{E}$$

London model of conductivity in superconducting materials; $\tau \rightarrow \infty$

$$m \frac{d\mathbf{v}}{dt} = -e\mathbf{E}$$

$$\frac{d\mathbf{v}}{dt} = -\frac{e\mathbf{E}}{m} \qquad \frac{d\mathbf{J}}{dt} = -ne \frac{d\mathbf{v}}{dt} = \frac{ne^2\mathbf{E}}{m}$$

From Maxwell's equations:

$$\nabla \times \mathbf{B} = \frac{4\pi}{c}\mathbf{J} + \frac{1}{c} \frac{\partial \mathbf{E}}{\partial t}$$

$$\nabla \times \mathbf{E} = -\frac{1}{c} \frac{\partial \mathbf{B}}{\partial t}$$

Properties of a normal metal

Drude model of conductivity in "normal" materials

$$m \frac{d\mathbf{v}}{dt} = -e\mathbf{E} - m \frac{\mathbf{v}}{\tau}$$

$$\mathbf{v}(t) = \mathbf{v}_0 e^{-t/\tau} - \frac{e\mathbf{E}\tau}{m}$$

$$\mathbf{J} = -nev; \quad \text{for } t \gg \tau \quad \Rightarrow \quad \mathbf{J} = \frac{ne^2\tau}{m} \mathbf{E} \equiv \sigma \mathbf{E}$$

Does this model allow for any temperature dependence on the resistivity?

1. No.
2. Yes.
3. Maybe.

London model of conductivity in superconducting materials; $\tau \rightarrow \infty$

$$m \frac{d\mathbf{v}}{dt} = -e\mathbf{E}$$

$$\frac{d\mathbf{v}}{dt} = -\frac{e\mathbf{E}}{m} \qquad \frac{d\mathbf{J}}{dt} = -ne \frac{d\mathbf{v}}{dt} = \frac{ne^2\mathbf{E}}{m}$$

From Maxwell's equations:

$$\nabla \times \mathbf{B} = \frac{4\pi}{c} \mathbf{J} + \frac{1}{c} \frac{\partial \mathbf{E}}{\partial t}$$

$$\nabla \times \mathbf{E} = -\frac{1}{c} \frac{\partial \mathbf{B}}{\partial t}$$

How is the London model different from the Drude model?

1. Subtle difference.
2. Big difference.



Some phenomenological theories < 1957

London model of conductivity in superconducting materials

$$\frac{d\mathbf{J}}{dt} = -ne \frac{d\mathbf{v}}{dt} = \frac{ne^2 \mathbf{E}}{m}$$

From Maxwell's equations:

$$\nabla \times \mathbf{B} = \frac{4\pi}{c} \mathbf{J} + \frac{1}{c} \frac{\partial \mathbf{E}}{\partial t} \quad \nabla \times \mathbf{E} = -\frac{1}{c} \frac{\partial \mathbf{B}}{\partial t}$$

$$\nabla \times (\nabla \times \mathbf{B}) = -\nabla^2 \mathbf{B} = \frac{4\pi}{c} \nabla \times \mathbf{J} - \frac{1}{c^2} \frac{\partial^2 \mathbf{B}}{\partial t^2}$$

$$-\nabla^2 \frac{\partial \mathbf{B}}{\partial t} = \frac{4\pi}{c} \nabla \times \frac{\partial \mathbf{J}}{\partial t} - \frac{1}{c^2} \frac{\partial^3 \mathbf{B}}{\partial t^3}$$

$$-\nabla^2 \frac{\partial \mathbf{B}}{\partial t} = \frac{4\pi ne^2}{mc} \nabla \times \mathbf{E} - \frac{1}{c^2} \frac{\partial^3 \mathbf{B}}{\partial t^3}$$

$$-\nabla^2 \frac{\partial \mathbf{B}}{\partial t} = -\frac{4\pi ne^2}{mc^2} \frac{\partial \mathbf{B}}{\partial t} - \frac{1}{c^2} \frac{\partial^3 \mathbf{B}}{\partial t^3}$$

$$\frac{\partial}{\partial t} \left(\nabla^2 - \frac{1}{\lambda_L^2} - \frac{1}{c^2} \frac{\partial^2}{\partial t^2} \right) \mathbf{B} = 0$$

$$\text{with } \lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$$

Are these equations

1. Exact?
2. Approximate?
3. Wrong?



London model – continued

London model of conductivity in superconducting materials

$$\frac{d\mathbf{J}}{dt} = -ne \frac{d\mathbf{v}}{dt} = \frac{ne^2 \mathbf{E}}{m}$$

$$\frac{\partial}{\partial t} \left(\nabla^2 - \frac{1}{\lambda_L^2} - \frac{1}{c^2} \frac{\partial^2}{\partial t^2} \right) \mathbf{B} = 0 \quad \text{with } \lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$$

For slowly varying solution:

$$\frac{\partial}{\partial t} \left(\nabla^2 - \frac{1}{\lambda_L^2} \right) \mathbf{B} = 0 \quad \text{for } \frac{\partial \mathbf{B}}{\partial t} = \hat{\mathbf{z}} \frac{\partial B_z(x, t)}{\partial t} :$$

$$\Rightarrow \frac{\partial B_z(x, t)}{\partial t} = \frac{\partial B_z(0, t)}{\partial t} e^{-x/\lambda_L}$$

Here we assume we know the boundary value at $x=0$.

London's leap: $B_z(x, t) = B_z(0, t) e^{-x/\lambda_L}$

Consistent results for current density:

$$\frac{4\pi}{c} \nabla \times \mathbf{J} = -\nabla^2 \mathbf{B} = -\frac{1}{\lambda_L^2} \mathbf{B} \quad \mathbf{J} = \hat{\mathbf{y}} J_y(x) \quad \Rightarrow \quad J_y(x) = \lambda_L \frac{ne^2}{mc} B_z(0) e^{-x/\lambda_L}$$

London model – continued

Penetration length for superconductor: $\lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$ Typically, $\lambda_L \approx 10^{-7} m$

$$B_z(x, t) = B_z(0, t)e^{-x/\lambda_L}$$

Vector potential for $\mathbf{B} = \nabla \times \mathbf{A}$ and $\nabla \cdot \mathbf{A} = 0$:

$$\text{Note that: } \nabla \times \mathbf{B} = \frac{4\pi}{c} \mathbf{J}$$


$$\mathbf{A} = \hat{\mathbf{y}} A_y(x)$$

$$A_y(x) = -\lambda_L B_z(0) e^{-x/\lambda_L}$$

$$-\nabla^2 \mathbf{A} = \frac{4\pi}{c} \mathbf{J} \Rightarrow \nabla^2 \mathbf{A} + \frac{4\pi}{c} \mathbf{J} = 0$$

Recall form for current density: $J_y(x) = \lambda_L \frac{ne^2}{mc} B_z(0) e^{-x/\lambda_L}$

$$\Rightarrow \mathbf{J} + \frac{ne^2}{mc} \mathbf{A} = 0 \quad \text{or} \quad \frac{ne}{m} \left(m\mathbf{v} + \frac{e}{c} \mathbf{A} \right) = 0$$

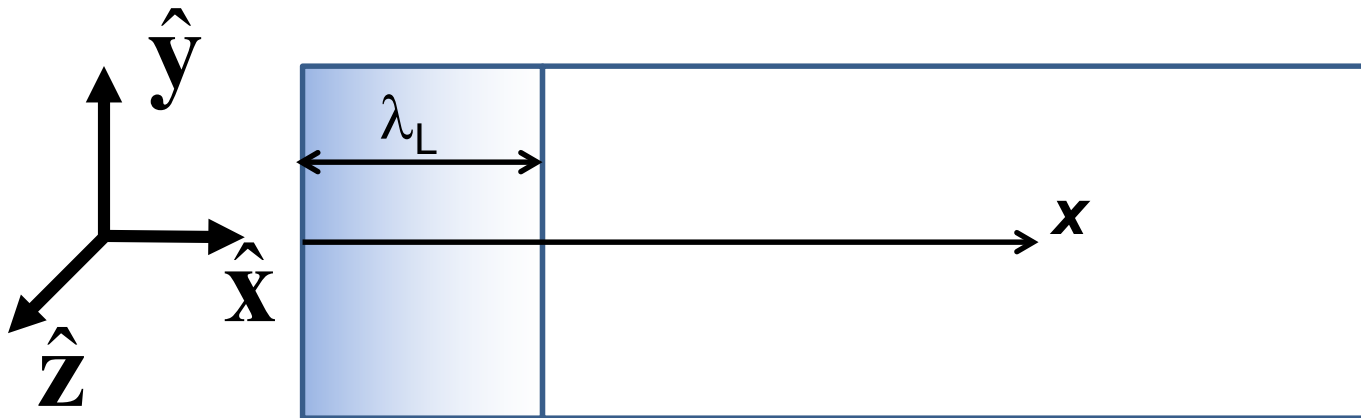

Behavior of superconducting material – exclusion of magnetic field according to the London model

Penetration length for superconductor: $\lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$

$$B_z(x, t) = B_z(0, t)e^{-x/\lambda_L}$$


Vector potential for $\nabla \cdot \mathbf{A} = 0$:

$$\mathbf{A} = \hat{\mathbf{y}}A_y(x) \quad A_y(x) = -\lambda_L B_z(0)e^{-x/\lambda_L}$$

$$\text{Current density: } J_y(x) = \lambda_L \frac{ne^2}{mc} B_z(0)e^{-x/\lambda_L}$$

$$\Rightarrow \mathbf{J} + \frac{ne^2}{mc} \mathbf{A} = 0 \quad \text{or} \quad \frac{ne}{m} \left(m\mathbf{v} + \frac{e}{c} \mathbf{A} \right) = 0$$

Typically, $\lambda_L \approx 10^{-7} m$

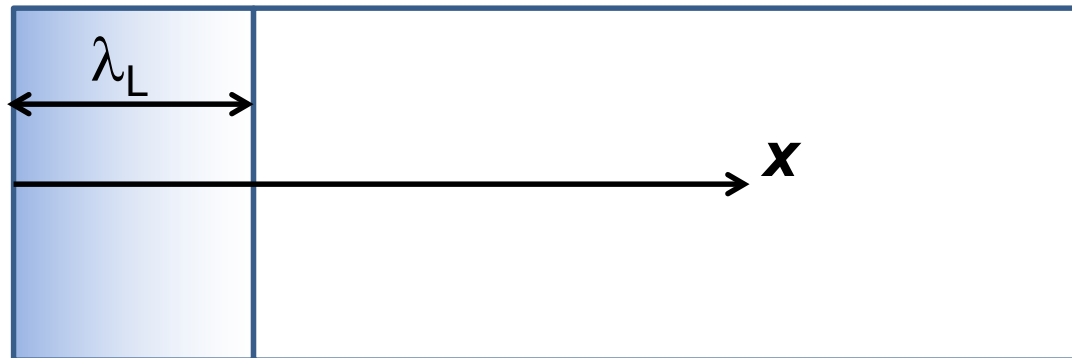

Behavior of magnetic field lines near superconductor


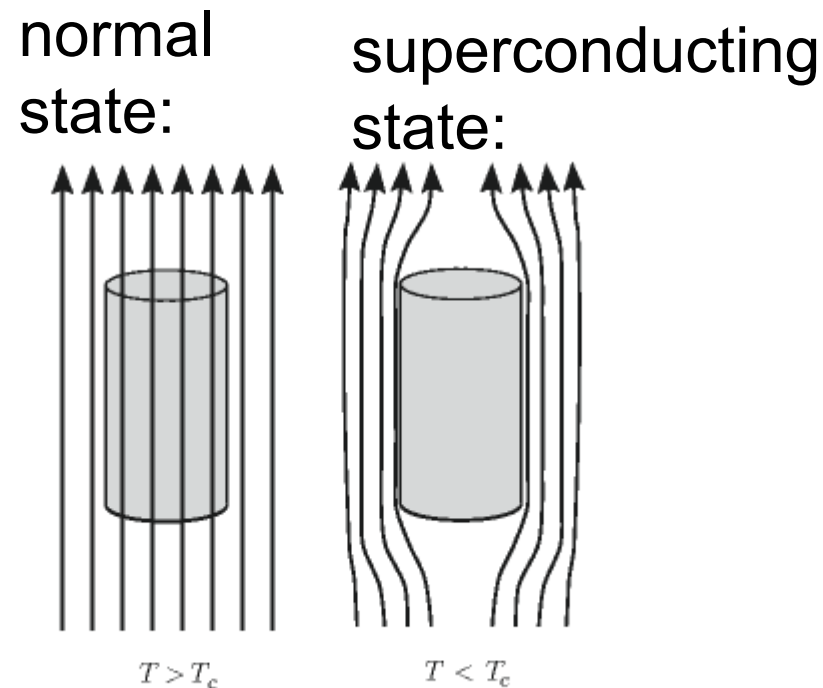


Figure 18.2 Exclusion of a weak external magnetic field from the interior of a superconductor.



The Meissner Effect



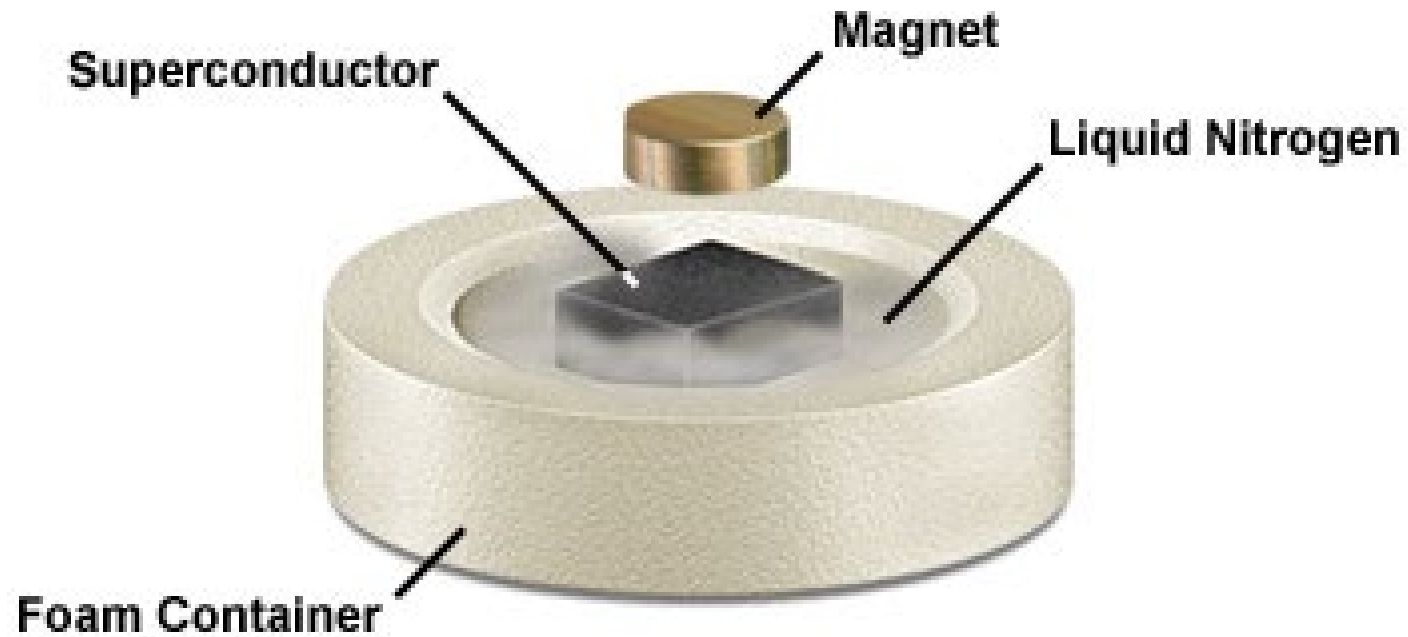

Need to consider phase equilibria between “normal” and superconducting state as a function of temperature and applied magnetic fields.

$$\mathbf{B} = \mathbf{H} + 4\pi\mathbf{M}$$

Within the superconductor, if $\mathbf{B} = 0$

$$\text{then } \mathbf{H} + 4\pi\mathbf{M} = 0 \quad \text{or} \quad \mathbf{M} = -\frac{\mathbf{H}}{4\pi}$$

Magnetization field

Treating London current in terms of corresponding magnetization field \mathbf{M} :

$$\mathbf{B} = \mathbf{H} + 4\pi\mathbf{M}$$

Here H is thought of in terms of an applied field.

$$\Rightarrow \text{For } x \gg \lambda_L, \quad \mathbf{H} = -4\pi\mathbf{M}, \quad \mathbf{M}(\mathbf{H}) = -\frac{\mathbf{H}}{4\pi}$$

Gibbs free energy associated with magnetization for superconductor:

$$G_S(H_a) = G_S(H=0) - \int_0^{H_a} dH M(H) = G_S(0) - \int_0^{H_a} dH \left(\frac{-H}{4\pi} \right) = G_S(0) + \frac{1}{8\pi} H_a^2$$

This relation is true for an applied field $H_a \leq H_C$ when the superconducting and normal Gibbs free energies are equal:

$$G_S(H_C) = G_N(H_C) \approx G_N(H=0)$$

Condition at phase boundary between normal and superconducting states:


$$G_N(H_C) \approx G_N(0) = G_S(H_C) = G_S(0) + \frac{1}{8\pi} H_C^2 \quad \text{At } T=0K$$

$$\Rightarrow G_S(0) - G_N(0) = -\frac{1}{8\pi} H_C^2$$

$$G_S(H_a) - G_N(H_a) = \begin{cases} -\frac{1}{8\pi} (H_C^2 - H_a^2) & \text{for } H_a < H_C \\ 0 & \text{for } H_a > H_C \end{cases}$$





Magnetization field (for “type I” superconductor)

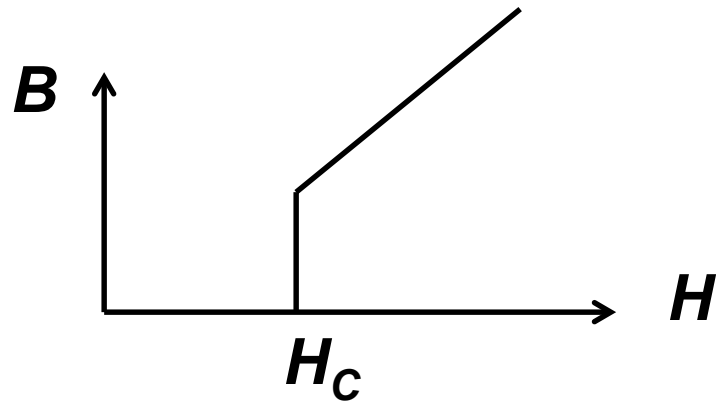

Inside superconductor

$$\mathbf{B}=0=\mathbf{H}+4\pi\mathbf{M} \text{ for } H < H_C$$

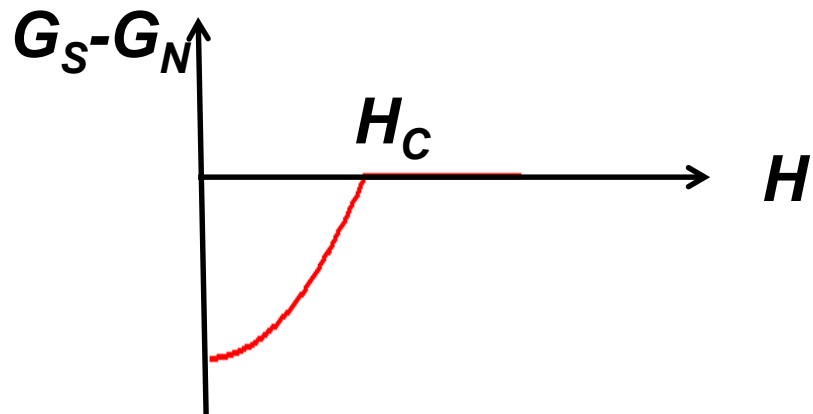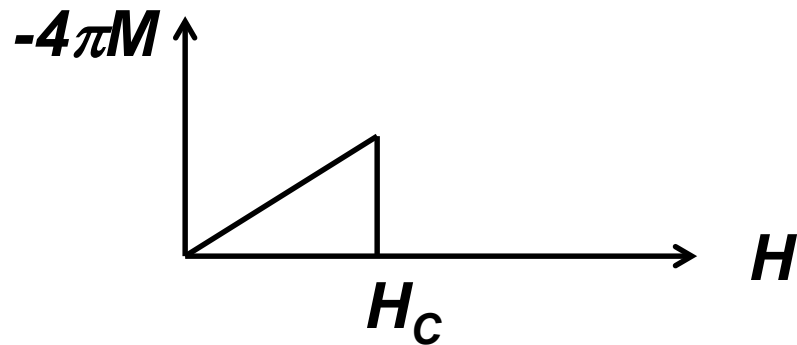

Theory of Superconductivity*

J. BARDEEN, L. N. COOPER,[†] AND J. R. SCHRIEFFER[‡]
Department of Physics, University of Illinois, Urbana, Illinois
(Received July 8, 1957)

$$G_S(0) - G_N(0) = -\frac{H_C^2}{8\pi} \approx -2N(E_F)(\hbar\omega)^2 e^{-2/(N(E_F)V)}$$

characteristic
phonon energy

density of electron
states at E_F

attraction potential
between electron
pairs



Temperature dependence of critical field

$$H_c(T) \approx H_c(0) \left(1 - \left(\frac{T}{T_c} \right)^2 \right)$$

From PR **108**, 1175 (1957)

Bardeen, Cooper, and Schrieffer, "Theory of Superconductivity"

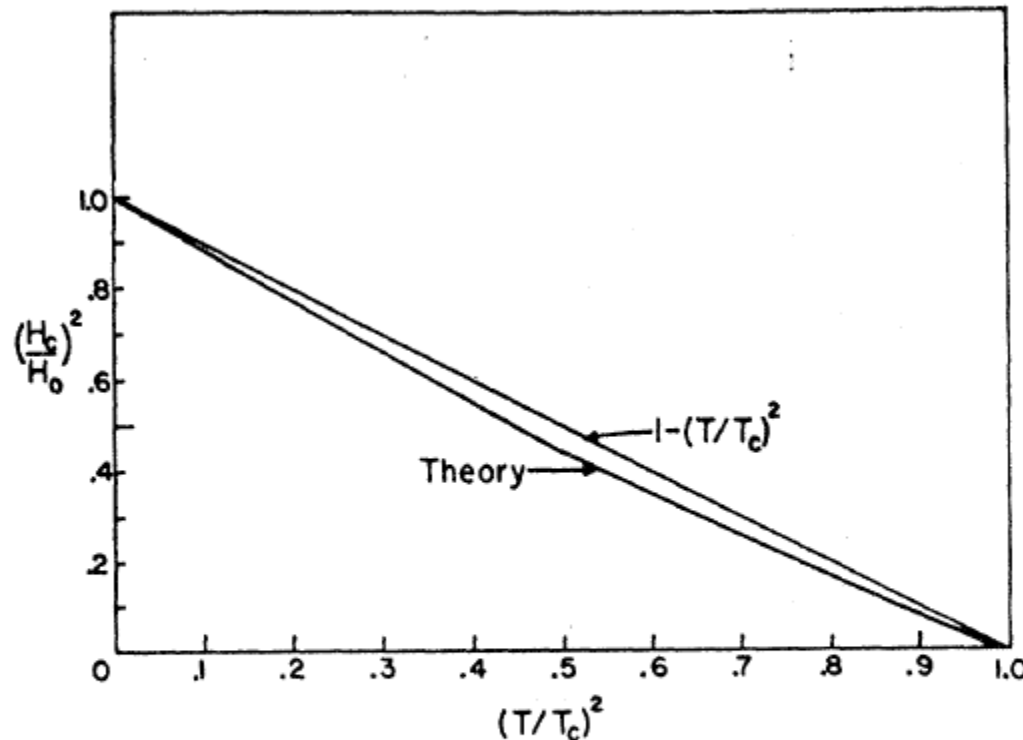


FIG. 2. Ratio of the critical field to its value at $T=0^\circ\text{K}$ vs $(T/T_c)^2$. The upper curve is the $1 - (T/T_c)^2$ law of the Gorter-Casimir theory and the lower curve is the law predicted by the theory in the weak-coupling limit. Experimental values generally lie between the two curves.

$$T_c \approx \frac{\hbar \omega}{k} e^{-2/(N(E_F)V)}$$

characteristic
phonon energy

density of electron
states at E_F

attraction potential
between electron
pairs



Type I elemental superconductors

<http://wuphys.wustl.edu/~jss/NewPeriodicTable.pdf>

Periodic Table of Superconductivity

(dedicated to the memory of Bernd Matthias; compiled by James S. Schilling)

30 elements superconduct at ambient pressure, 23 more superconduct at high pressure.

H		ambient pressure superconductor										high pressure superconductor										He					
Li 0.0004 14 30	Be 0.026 3.7 30	<div>T_c(K) T_c^{max}(K) P(GPa)</div>										<div>T_c^{max}(K) P(GPa)</div>										B 11 250	C	N	O 0.6 100	F	Ne
Na	Mg																					Al 1.14	Si 8.2 15.2	P 13 30	S 17.3 190	Cl	Ar
K	Ca 29 217	Sc 19.6 106	Ti 0.39 3.35 56.0	V 5.38 16.5 120	Cr	Mn	Fe 2.1 21	Co	Ni	Cu	Zn 0.875	Ga 1.091 7 1.4	Ge 5.35 11.5	As 2.4 32	Se 8 150	Br 1.4 100	Kr										
Rb	Sr 7 50	Y 19.5 115	Zr 0.546 11 30	Nb 9.50 9.9 10	Mo 0.92	Tc 7.77	Ru 0.51	Rh .00033	Pd	Ag	Cd 0.56	In 3.404	Sn 3.722 5.3 11.3	Sb 3.9 25	Te 7.5 35	I 1.2 25	Xe										
Cs 1.3 12	Ba 5 18	insert La-Lu	Hf 0.12 8.6 62	Ta 4.483 4.5 43	W 0.012	Re 1.4	Os 0.655	Ir 0.14	Pt	Au	Hg-α 4.153	Tl 2.39	Pb 7.193	Bi 8.5 9.1	Po	At	Rn										
Fr	Ra	insert Ac-Lr	Rf	Ha																							
		La-fcc 6.00 13 15	Ce 1.7 5	Pr	Nd	Pm	Sm	Eu 2.75 142	Gd	Tb	Dy	Ho	Er	Tm	Yb	Lu 12.4 174											
		Ac	Th 1.368	Pa 1.4	U 0.8(β) 2.4(α) 1.2	Np	Pu	Am 0.79 2.2 6	Cm	Bk	Cf	Es	Fm	Md	No	Lr											

M. Debossai, T. Matsuoka, J.J. Hamlin, W. Bi, Y. Meng, K. Shimizu, and J.S. Schilling, J. Phys.: Conf. Series **215**, 012034 (2010).
High pressure data for Ca and Be: K. Shimizu email from 9 Dec 2013.

04/25/2022

PHY 712 Spring 2022 -- Lecture 33

20

Type I superconductors:

$$H_c(T) = H_c(0) \left(1 - \frac{T^2}{T_c^2}\right)$$

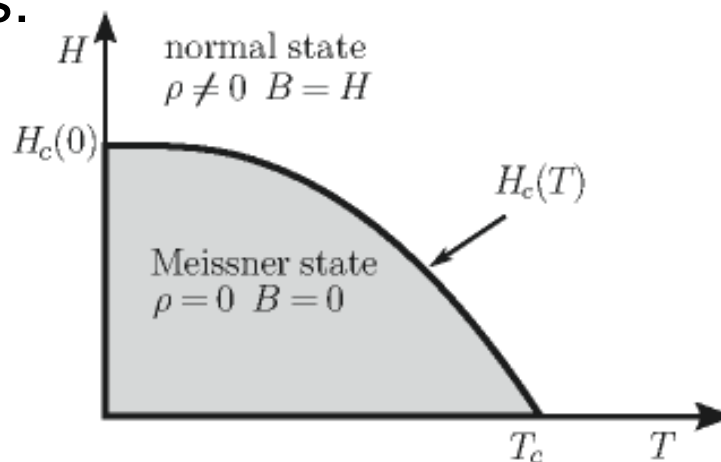


Figure 18.3 Schematic phase diagram illustrating normal and superconducting regions of a type-I superconductor.

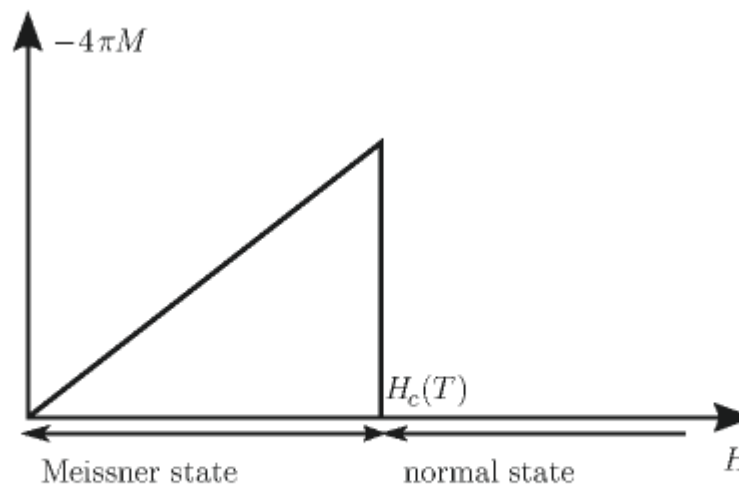


Figure 18.4 Magnetization versus applied field for type-I superconductors.

The following slides give a quick look of some of the intriguing aspects of superconducting materials and their properties --

Type II superconductors

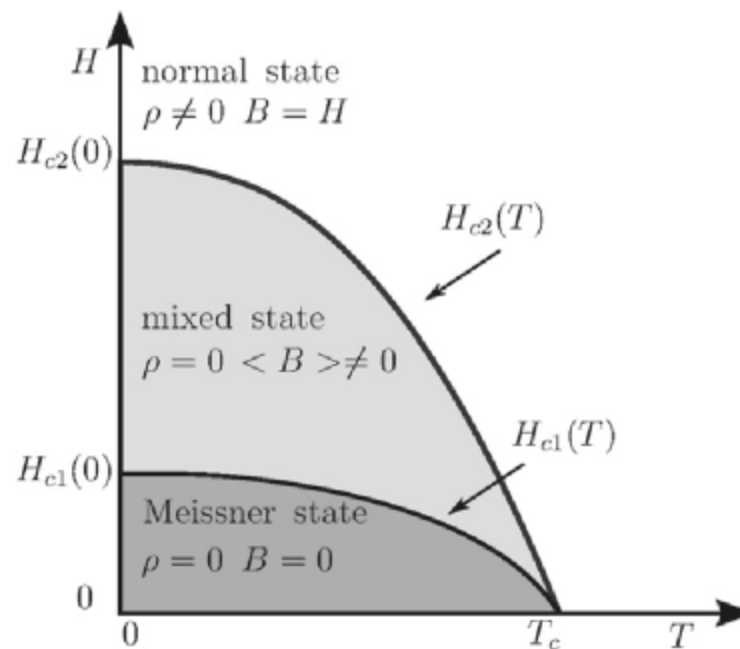


Figure 18.5 Schematic phase diagram illustrating normal, mixed and Meissner regions of a type-II superconductor (the vanishingly small resistivity of the mixed state occurs if flux lines are “pinned” by appropriate material defects); in the mixed state, $\langle B \rangle$ denotes the average magnetic field in the superconductor.

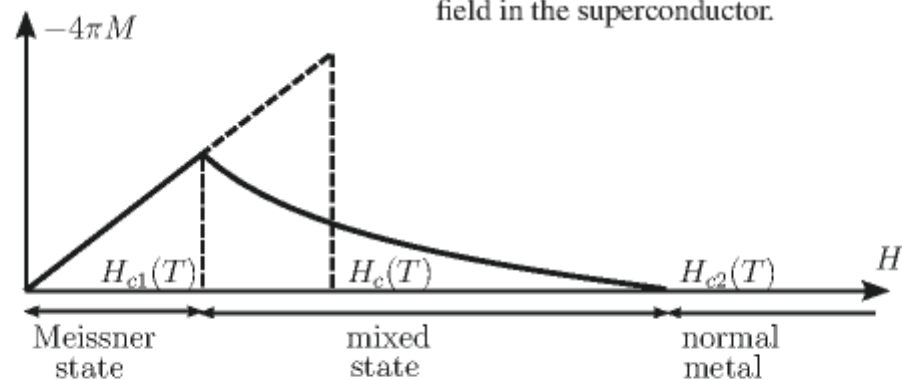


Figure 18.6 Magnetization versus applied field H for a type-II superconductor. The equivalent area construction of the thermodynamic field $H_c(T)$ is also illustrated.



Quantization of current flux associated with the superconducting state (Ref: Ashcroft and Mermin, ***Solid State Physics***)

From the London equations for the interior of the superconductor:

$$\left(m\mathbf{v} + \frac{e}{c} \mathbf{A} \right) = 0$$

Now suppose that the current carrier is a pair of electrons characterized by a wavefunction of the form $\psi = |\psi| e^{i\phi}$

The quantum mechanical current associated with the electron pair is

$$\begin{aligned} \mathbf{j} &= -\frac{e\hbar}{2mi} (\psi^* \nabla \psi - \psi \nabla \psi^*) - \frac{2e^2}{mc} \mathbf{A} |\psi|^2 \\ &= -\left(\frac{e\hbar}{m} \nabla \phi + \frac{2e^2}{mc} \mathbf{A} \right) |\psi|^2 \end{aligned}$$

Quantization of current flux associated with the superconducting state -- continued



Suppose a superconducting material has a cylindrical void. Evaluate the integral of the current in a closed path within the superconductor containing the void.

$$\oint \mathbf{j} \cdot d\mathbf{l} = 0 = -\oint \left(\frac{e\hbar}{m} \nabla \phi + \frac{2e^2}{mc} \mathbf{A} \right) |\psi|^2 \cdot d\mathbf{l}$$

$$\oint \mathbf{A} \cdot d\mathbf{l} = \int (\nabla \times \mathbf{A}) \cdot d\mathbf{a} = \int \mathbf{B} \cdot d\mathbf{a} = \Phi \quad \text{magnetic flux}$$

$$\oint \nabla \phi \cdot d\mathbf{l} = 2\pi n \quad \text{for some integer } n$$

$$\Rightarrow \text{Quantization of flux in the void: } |\Phi| = n \frac{hc}{2e} \equiv n\Phi_0$$

Such “vortex” fields can exist within type II superconductors.



Table 18.1 Critical temperature of some selected superconductors, and zero-temperature critical field. For elemental materials, the thermodynamic critical field $H_c(0)$ is given in gauss. For the compounds, which are type-II superconductors, the upper critical field $H_{c2}(0)$ is given in Tesla ($1 \text{ T} = 10^4 \text{ G}$). The data for metallic elements and binary compounds of V and Nb are taken from G. Burns (1992). The data for MgB_2 and iron pnictide are taken from the references cited in the text, and refer to the two principal crystallographic axes. The data for the other compounds are taken from D. R. Harshman and A. P. Mills, Phys. Rev. B 45, 10684 (1992)]. A more extensive list of data can be found in the mentioned references.

Metallic elements	$T_c(K)$	$H_c(0)$ (gauss)
Al	1.17	105
Sn	3.72	305
Pb	7.19	803
Hg	4.15	411
Nb	9.25	2060
V	5.40	1410
Binary compounds	$T_c(K)$	$H_{c2}(0)$ (Tesla)
V_3Ga	16.5	27
V_3Si	17.1	25
Nb_3Al	20.3	34
Nb_3Ge	23.3	38
MgB_2	40	≈ 5 ; ≈ 20
Other compounds	$T_c(K)$	$H_{c2}(0)$ (Tesla)
UPt_3 (heavy fermion)	0.53	2.1
PbMo_6S_8 (Chevrel phase)	12	55
$\kappa\text{--}[\text{BEDT--TTF}]_2\text{Cu}[\text{NCS}]_2$ (organic phase)	10.5	≈ 10
$\text{Rb}_2\text{CsC}_{60}$ (fullerene)	31.3	≈ 30
$\text{NdFeAsO}_{0.7}\text{F}_{0.3}$ (iron pnictide)	47	≈ 30 ; ≈ 50
Cuprate oxides	$T_c(K)$	$H_{c2}(0)$ (Tesla)
$\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ($x \approx 0.15$)	38	≈ 45
$\text{YBa}_2\text{Cu}_3\text{O}_7$	92	≈ 140
$\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$	89	≈ 107
$\text{Tl}_2\text{Ba}_2\text{Ca}_2\text{Cu}_3\text{O}_{10}$	125	≈ 75



Crystal structure of one of the high temperature superconductors


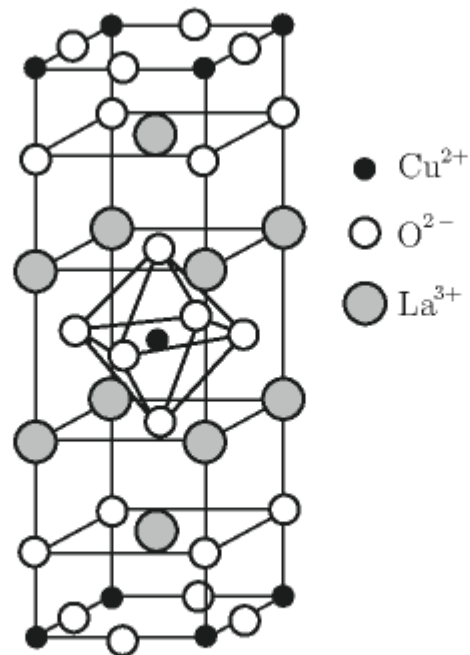


Figure 18.1 Crystal structure of the ceramic material La_2CuO_4 . Appropriately doped, lanthanum-based cuprates opened the path to high- T_c superconductivity in 1986.

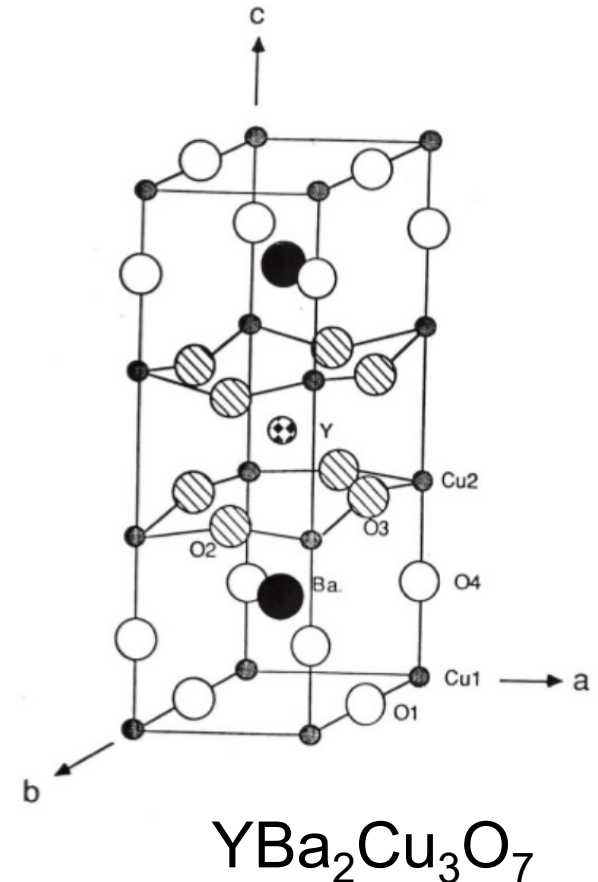

From MS thesis of Brent
Howe (Minn State U, 2014)

Some details of single vortex in type II superconductor

London equation without vortices:

$$\frac{4\pi}{c} \nabla \times \mathbf{J} = -\nabla^2 \mathbf{B} = -\frac{1}{\lambda_L^2} \mathbf{B} \quad \text{where} \quad \lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$$

Equation for field with single quantum of vortex along z - axis:

$$\nabla^2 \mathbf{B} - \frac{1}{\lambda_L^2} \mathbf{B} = -\frac{\Phi_0}{\lambda_L^2} \hat{\mathbf{z}} \delta(\mathbf{r}) \quad \Phi_0 = \frac{hc}{2e} \quad \mathbf{r} = x\hat{\mathbf{x}} + y\hat{\mathbf{y}}$$

$$\text{Solution:} \quad \mathbf{B}(\mathbf{r}) = \hat{\mathbf{z}} \frac{\Phi_0}{2\pi\lambda_L^2} K_0\left(\frac{r}{\lambda_L}\right)$$


Check:

$$\text{For } r > 0 \quad \left(\frac{d^2}{dr^2} + \frac{1}{r} \frac{d}{dr} - \frac{1}{\lambda_L^2} \right) K_0\left(\frac{r}{\lambda_L}\right) = 0$$


$$\text{For } r \rightarrow 0 \quad 2\pi \int_0^r dr' r' \left(\frac{d^2}{dr'^2} + \frac{1}{r'} \frac{d}{dr'} - \frac{1}{\lambda_L^2} \right) K_0\left(\frac{r'}{\lambda_L}\right) = -2\pi$$

$$\text{Since } K_0(u) \underset{u \rightarrow 0}{\approx} -\ln u$$

$$\mathbf{B}(\mathbf{r}) = \hat{\mathbf{z}} \frac{\Phi_0}{2\pi\lambda_L^2} K_0\left(\frac{r}{\lambda_L}\right)$$

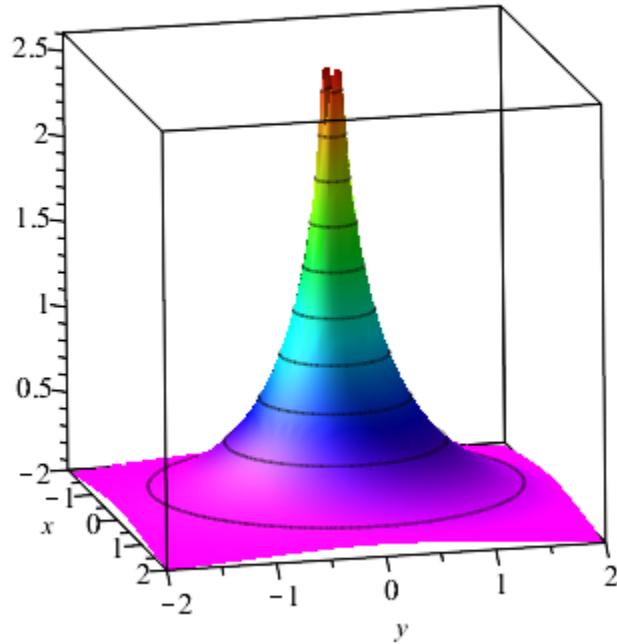

Scanning probe images of vortices in YBCO at 22 K

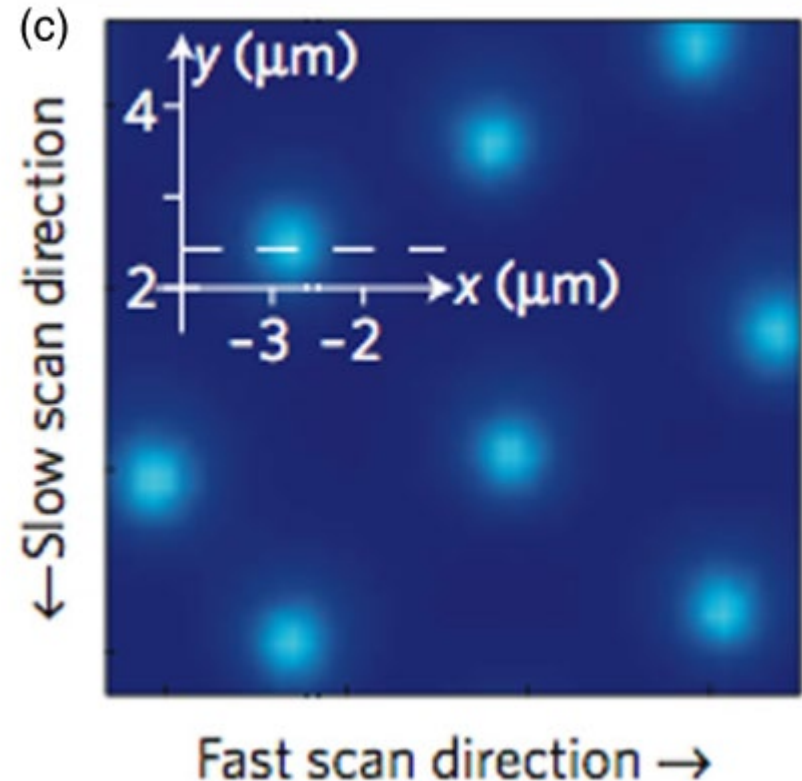

Fundamental studies of superconductors using scanning magnetic imaging

J R Kirtley

Center for Probing the Nanoscale, Stanford University, Stanford, CA, USA

Based on physics of the Josephson junction.